



Effective removal of heavy metals from industrial sludge with the aid of a biodegradable chelating ligand GLDA



Qing Wu, Yanrui Cui, Qilu Li, Jianhui Sun*

School of Environment, Henan Normal University, Key Laboratory for Yellow River and Huai River Water Environmental and Pollution Control, Ministry of Education, Henan Key Laboratory for Environmental Pollution Control, No. 46, Jianshe Road, Xinxiang 453007, Henan, China

HIGHLIGHTS

- A novel readily biodegradable chelating ligand was employed to remove heavy metals.
- The effects of different conditions on the extraction with GLDA were probed.
- Species distribution of metals before and after extraction with GLDA was analyzed.
- GLDA was effective for Cd extraction from sludge samples under various conditions.
- GLDA offers special insights in the effective removal of heavy metals.

ARTICLE INFO

Article history:

Received 29 June 2014

Received in revised form

25 September 2014

Accepted 21 October 2014

Available online 29 October 2014

Keywords:

Tetrasodium of *N,N* bis(carboxymethyl)

glutamic acid

Heavy metal

Industrial sludge

Biodegradable chelating ligand

ABSTRACT

Tetrasodium of *N,N* bis(carboxymethyl) glutamic acid (GLDA), a novel readily biodegradable chelating ligand, was employed for the first time to remove heavy metals from industrial sludge generated from a local battery company. The extraction of cadmium, nickel, copper, and zinc from battery sludge with the presence of GLDA was studied under different experimental conditions such as contact times, pH values, as well as GLDA concentrations. Species distribution of metals in the sludge sample before and after extraction with GLDA was also analyzed. Current investigation showed that (i) GLDA was effective for Cd extraction from sludge samples under various conditions. (ii) About 89% cadmium, 82% nickel and 84% copper content could be effectively extracted at the molar ratio of GLDA:M(II) = 3:1 and at pH = 4, whereas the removal efficiency of zinc was quite low throughout the experiment. (iii) A variety of parameters, such as contact time, pH values, the concentration of chelating agent, stability constant, as well as species distribution of metals could affect the chelating properties of GLDA.

2014 Elsevier B.V. All rights reserved.

1. Introduction

High level of heavy metal residues in sludge is one of the major obstacles for the sludge disposal. The techniques currently employed for wastewater treatment result in the generation of large quantities of sludge that needs to be disposed off [1]. One of the most potential routes for sludge disposal (especially the sewage sludge) is the land application by recycling of the valuable components (nitrogen/phosphorus contained species, and organic matters) within the sludge [2]. However, industrial sludge generated from the battery factories, metal plating facilities as well as tanneries contains large amounts of heavy metals [3]. It is well known that several types of metals, such as chromium, copper,

lead, mercury, and cadmium, are particularly harmful and toxic to human beings and ecological environments [4]. They can accumulate in living organisms, causing various diseases and disorders. They are also non biodegradable and could remain indefinitely in the soil environment [5,6]. In most of the developing countries, the sludge disposal on nearby uncultivated lands is fairly universal. Such practices certainly lead to heavy metal contamination of the biosphere [7,8]. In this regard, the effective removal and regeneration of heavy metals from sludge is quite imperative.

Pioneer work on the removal of heavy metal ions was initiated by Dudinska and Juang [9,10] by using complex agents such as nitrilotriacetic acid (NTA), citric acid (CA), and ethylenediaminetetraacetic acid (EDTA). In particular, EDTA has been proven as an effective chelating agent for heavy metal decontamination [11–13]. However, these agents can pose a high risk of metal leaching to the groundwater due to their refractory nature [14]. Hence, replacement of such ligands by more environmental friendly

* Corresponding author. Tel.: +86 373 3325971.

E-mail addresses: sunjh@htu.cn, sunjhhj@163.com (J. Sun).

ones would be highly desirable. To this end, tetrasodium of *N,N*-bis(carboxymethyl) glutamic acid (GLDA) has been introduced as a biodegradable chelant, where its production is based on a green chemistry process involving the fermentation of readily available corn sugars [15]. GLDA exhibits good chelating capacity towards a plethora of metal ions, it also possesses excellent biodegradability, with more than 60% of GLDA degraded within 28 days [16]. Another notable feature is that the ecological footprint of GLDA is far smaller than those from traditional counterparts because of its efficient manufacturing process [17]. Previous studies with regard to the usage of GLDA have centered on its applications in terms of detergents, cosmetics, and boosting agents for disinfecting products [18]. To the best of our knowledge, utilizing GLDA as a chelating reagent to remove heavy metals from industrial sludge has not been reported so far.

There are large amounts of cadmium and nickel present in the industrial sludge, which has recently become a focus of our research. As priority environmental pollutants, cadmium and nickel have received more attention with respect to their transportation, decontamination, and biological enrichment [19–21]. To realize effective decontamination and removal of primary pollutants, getting a full grasp on their distribution/fraction is of great significance. It has been well received that the determination of the total amounts of elements does not give an accurate estimation of the potential environmental impact, since it is becoming apparent that both bioavailability and toxicity strongly depend on the chemical forms of heavy metals [22]. To date, Tessier [23] and BCR [24,25] (the Community Bureau of Reference, now the European Union “Measurement and Testing Programme”) sequential extraction methods have been widely applied to the field of metal fractionation to deal with different environmental samples [26]. Compared with others, BCR procedures possess better reproducibility, precision and achieve comparable performances [24]. In the typical BCR sequential extraction, the metal elements are divided into acid soluble, reducible, and oxidizable fractions. As for the modified BCR sequential extraction method, two additional fractions, water soluble and residual ones, are also considered.

In this work, GLDA has been utilized as an environmentally friendly chelating reagent to remove heavy metals from industrial sludge. The extraction performances were evaluated by the removal of cadmium, nickel, copper, and zinc from battery sludge, where the effects of pH value, contact time, molar ratio of GLDA/metal on the removal efficiency in the presence of GLDA

Table 2
Characterized heavy metal contents in the sludge compared to the legal standard.

Parameters (unit)	Value	Acid soil (pH < 6.5) ^a	Alkaline soil (pH ≥ 6.5) ^a	Environmental soils ^b
Water content (%)	98.5			
pH	11.5			
Cd (mg kg ⁻¹)	172,300	5	20	1
Ni (mg kg ⁻¹)	22,225	100	200	200
Zn (mg kg ⁻¹)	1700	2000	3000	500
Cu (mg kg ⁻¹)	237	800	1500	400
Ca (mg kg ⁻¹)	130,500			
Mg (mg kg ⁻¹)	9300			
Fe (mg kg ⁻¹)	56,750			

^a National Standard of the People's Republic of China GB 18918-2002: Discharge standard of pollutants for municipal wastewater treatment plant (mg kg⁻¹).

^b National Standard of the People's Republic of China GB 15618-1995: Environmental quality standard for soils (mg kg⁻¹).

through a 0.45 μm membrane filter. The solutions were properly stored at 4 °C prior to analysis.

2.4. Analytical methods

The pH value of the sludge sample was determined by employing a PHS 3C Professional pH meter (Shanghai, China). The sludge sample was pretreated by an SISP DS 360 graphite digestion apparatus (Guangzhou, China) with the aid of the concentrated HCl HNO₃ HF HClO₄ solution at 150–190 °C. The concentrations of the dissolved heavy metals in the digestion solutions and extraction solutions were measured by using an inductively coupled plasma mass spectrometry (PerkinElmer, USA). Species distribution of heavy metals in the sludge sample before and after extraction with GLDA was analyzed by the modified BCR sequential extraction method.

The extraction efficiency (%E) was calculated according to the following equation:

$$\%E = \frac{(V \times C)}{(M \times m)} \times 100\% \quad (1)$$

where *V* is the volume of the extraction solution (mL), *C* is the concentration of the metal dissolved in the extraction solution (μg L⁻¹), *M* is the mass of the sludge sample (g), and *m* is the concentration of the metal in the sludge sample (mg kg⁻¹).

The extraction and sequential extraction experiments were conducted from September 2013 to May 2014. A minimum of triplicate extraction runs and related analysis was made for all samples.

3. Results and discussion

3.1. Characterization of sludge

Table 2 displays the general information (water content, pH value, main metal species etc.) of the sludge sample obtained after detailed characterization. The molar sum of the heavy metals (Cd, Ni, Zn and Cu) in sludge is 1945 mmol kg⁻¹. The content of Cd and Ni is 172,300 and 22,225 mg kg⁻¹, respectively, both of which are beyond the environment quality standard for soils (1 and 200 mg kg⁻¹ for Cd and Ni, respectively) and the discharge standard of pollutants for municipal wastewater treatment plant in China (5 and 100 mg kg⁻¹ for acid soil where pH < 6.5, 20 and 200 mg kg⁻¹ for alkaline soil where pH > 6.5 for Cd and Ni, respectively). Disposal of such sludge on nearby unused lands would lead to serious heavy metal contaminations with a string of negative consequences for the biosphere.

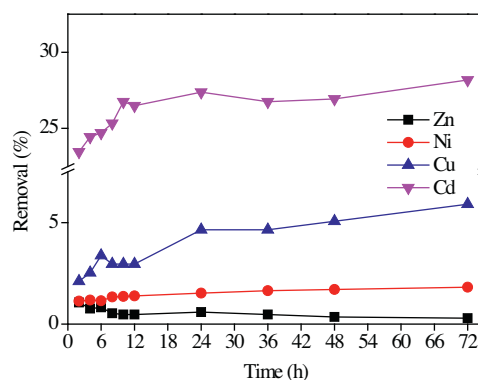


Fig. 1. Effect of contact time on the extraction of Cd, Ni, Cu and Zn. Conditions: GLDA:M(II) = 1:1, without pH adjustment (at a natural pH = 12).

3.2. Effect of contact time on the extraction

In order to attain optimum extraction performance of heavy metals, the effect of contact time on the removal efficiency was studied. Fig. 1 shows the kinetics of Cd, Ni, Cu, and Zn extraction from the sludge sample using GLDA (GLDA:M(II) = 1:1; pH = 12) with a reaction time of 72 h. It is obvious that the extraction of Cd and Cu exhibits a relatively fast initial step (within 24 h), followed by a smoother release of metals. Extraction of Ni and Zn are much slower than that of Cd or Cu. In general, our investigations showed that the extraction efficiency increased with the increasing of contact time, however, only slow increase was observed after 24 h (up to 72 h). Therefore, 24 h was chosen as the optimum reaction time for the subsequent experiments, the finding of which is also consistent with other reports regarding the extraction time [13]. This observation could be explained by the fact that the removal efficiency is not changed with the increase of contact time once the chelating process reaches equilibrium.

3.3. Effect of pH conditions on the extraction

The comparison study on the removal efficiency of Cd, Ni, Cu, and Zn at different pH values with/without the presence of GLDA was conducted. It is found that the removal efficiency of heavy metals decreases rapidly as pH value increases in the absence of GLDA (Fig. 2). Although a general trend goes that the values of the efficiencies are entirely augmented by the GLDA dosage over a wide pH range from 3 to 12, at GLDA:M(II) = 1:1, the removal efficiency of heavy metals still declines as pH value increases. The extraction efficiency at pH = 3 in the absence of GLDA is 24%, 17%, 57% and 24% for Cd, Ni, Cu and Zn, respectively, whilst under identical pH conditions, the efficiency with the presence of GLDA (GLDA:M(II) = 1:1) reaches 76%, 47%, 49% and 32% for Cd, Ni, Cu and Zn, respectively. It is interesting to note that the extraction efficiency of Cd is dramatically affected by the addition of GLDA under alkaline conditions. These results indicate that the pH conditions could exert a significant effect on the extraction efficiency, where strongly acidic conditions with the presence of GLDA are favorable for heavy metal removal.

At low concentrations of the chelating agent, metal extraction shows a strong dependence on pH values of the environment. At a large GLDA:M(II), the pH dependence of the extraction is much less prominent, this is reflected by the trend shown in Fig. 2, where the removal efficiency of heavy metals declines slowly as the pH value increases at a higher GLDA:M(II) = 5:1. Notably, amongst these metals, GLDA functions best with Cd over the whole pH range (the efficiencies are all above 72%), with the peak values occurred


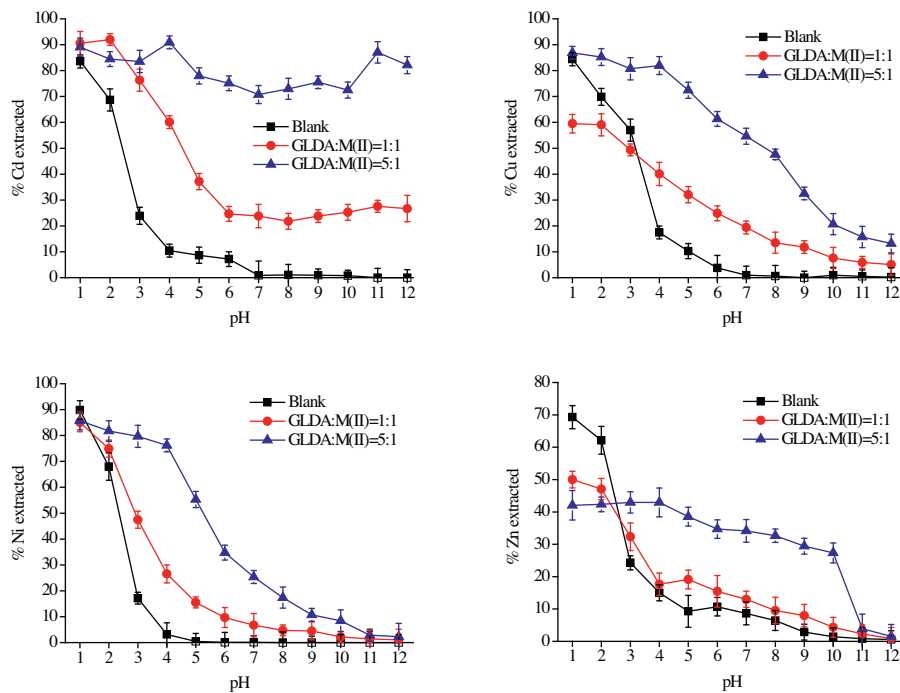


Fig. 2. Effect of the pH values on the extraction of Cd, Ni, Cu and Zn with three different conditions: in the absence of GLDA, in the presence of GLDA with GLDA:M(II) at 1:1 and 5:1.

at pH=4 and 11, whereas Cu and Ni maintains a good removal efficiency at pH ≤ 4, with the peak value occurred at pH=4.

To understand the metal ion removal with the aid of GLDA, it is necessary to take the metal ion ligand interaction into consideration. The complexation is characterized by the formation of stable 1:1 metal to ligand complexes as the major species [17]. The reaction between the metal ion and the anion of GLDA under different pH conditions can be interpreted as follows:



In paper [16], the stability constant (logK) of metal chelate with GLDA (L) were introduced and the sequence of chelating abilities were: $\log K_{CuL} (13.1) > \log K_{Fe(III)L} (11.7) > \log K_{NiL} (10.9) > \log K_{ZnL} (10.0) > \log K_{CdL} (9.1) > \log K_{Fe(II)L} (8.7) > \log K_{MgL} (6.1) > \log K_{CaL} (5.2)$. Apparently, GLDA possesses a strong capability to chelate Cu, Ni, Zn, and Cd. Therefore, it is easy to understand why GLDA can extract heavy metals from sludge quite effectively. However, actual extraction efficiency sequence in this work stays $Cd > Cu > Zn > Ni$ (GLDA:M(II) = 1), which is not consistent with the trend displayed above. This is due to the fact that the stability constant indicating the capability of forming complexes is determined under ideal conditions. However, in the case of real effluents, the impact of competitive parameters, especially the pH values of the environment, should be taken into account [28]. It would result in distinct efficiency sequence in reality compared to the theoretical one. The pH conditions can affect the stability and the effectiveness of the chelating system. The conditional stability constant (logK') is an indication of the stability of the complex as a function of the pH conditions, as shown in Fig. 3.

With respect to a higher GLDA:M(II) = 5:1, such pH dependence on the extraction efficiency seems weakened (Fig. 2). This suggests that the GLDA concentration is another important factor that affects the extraction of heavy metals. It has been shown in this study

that GLDA is a good metal extractant especially for Cd, however, an appropriate pH and GLDA concentration should be further verified to achieve optimal removal of heavy metals. Therefore, in the next stage of investigations, the solutions of the studied Cu, Zn, Cd and Ni complexes with GLDA possess the following pHs: 12–13 (without any additional adjustments), 11, 7, and 4, respectively.

3.4. Effect of GLDA concentration on the extraction

In order to examine the effect of GLDA concentrations (i.e. the molar ratio of GLDA to heavy metal) on the extraction of heavy metals, different molar ratios of GLDA:M(II) in the sludge ranging from 1:1 to 10:1 under different pH conditions were tested. Batch extraction experiments were carried out at the natural pH (pH=12~13), as well as at pH=11, 7, and 4, respectively. It can be observed in Fig. 4 that the extraction efficiencies of Cd increase prominently under all the extraction pH conditions with the increase of the GLDA concentrations. At the natural pH, the optimum extraction efficiencies of all metals reach at GLDA:M(II) = 9:1, where approx. 69%, 5%, 8%, and 1% of Cd, Ni, Cu, and Zn is extracted, respectively. The discrepancy between the theoretical ratio (1:1) and the obtained real ratio (9:1) regarding the optimum extraction

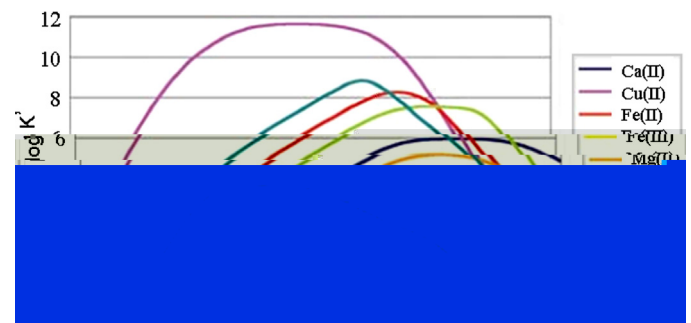
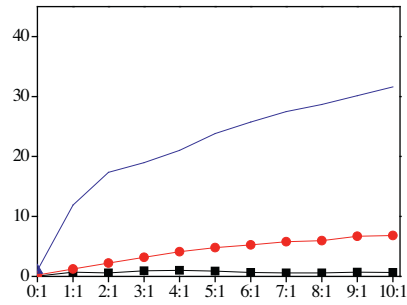
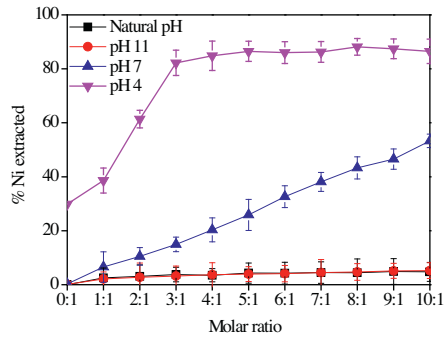
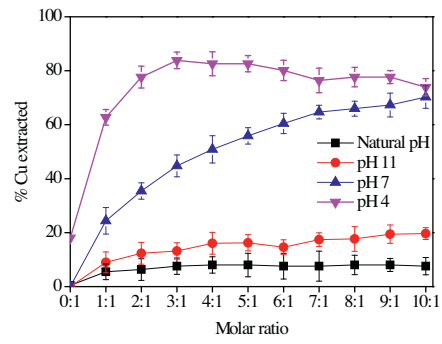
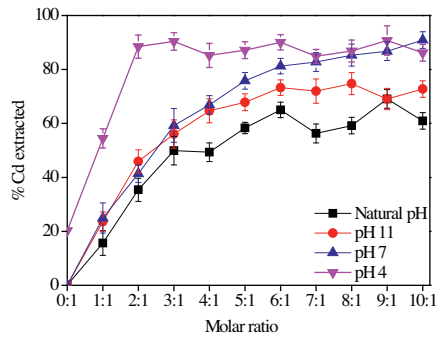


Fig. 3. Theoretical curves of the conditional stability constant (logK') of GLDA for various metal ions as a function of pH (1:1 metal:chelate complex). [18].



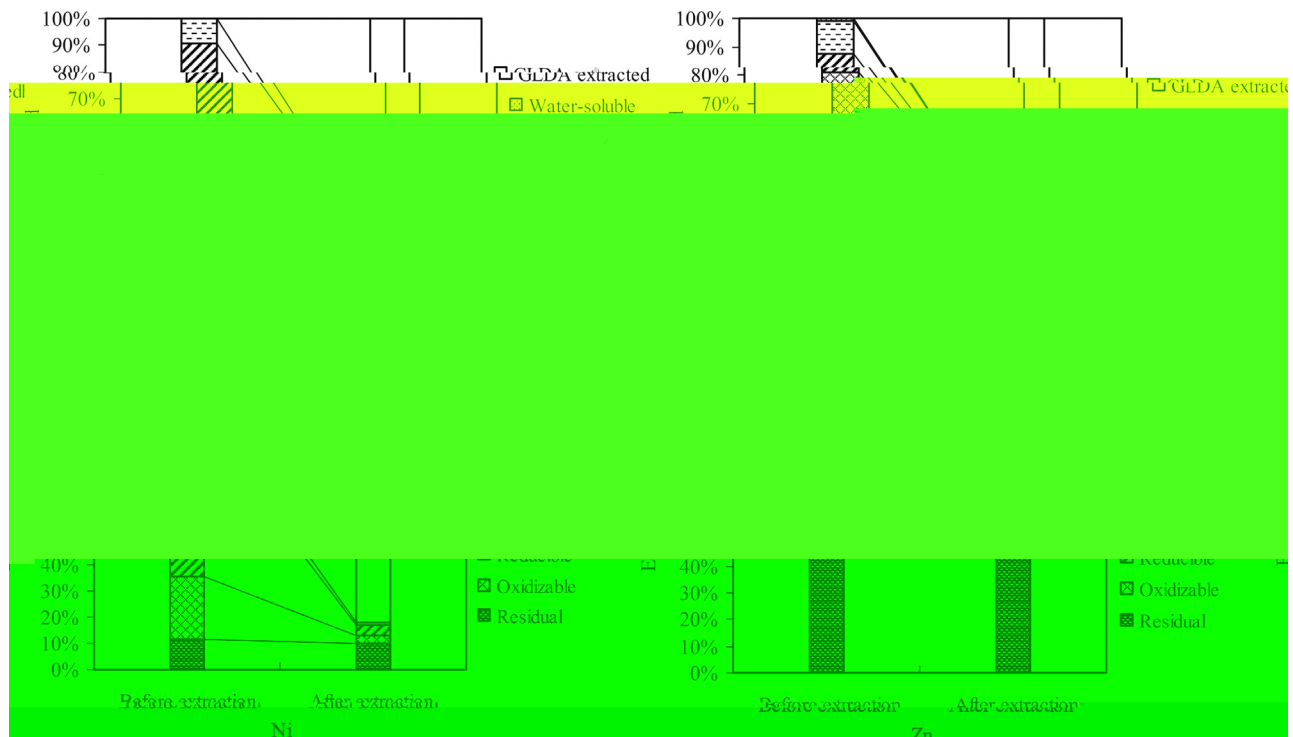


Fig. 5. Species distribution of Cd, Ni, Cu and Zn in the sludge sample before and after extraction with GLDA (extraction conditions: pH = 4, GLDA:M(II) = 3:1).

4. Conclusions

In summary, an environmentally friendly chelating reagent GLDA was employed to remove heavy metals from industrial sludge. The extraction performances were evaluated by the removal of cadmium, nickel, copper, and zinc from the sludge sample, where the effects of contact time, pH value, and molar ratio of GLDA/metal on the removal efficiency were probed. The chelating property was related not only to the stability constant, but also to species distribution of metals, pH conditions, contact time of reaction, as well as the concentrations of chelating agent *etc.* The extracted metals came mainly from reducible, acid soluble, water soluble, and oxidizable fractions, where about 89%, 82% and 84% of Cd, Ni and Cu content in the sample was extracted under optimum conditions (pH = 4, GLDA:M(II) = 3:1), respectively. The low extraction efficiency of Zn was attributed to the fact that nearly 60% of Zn existed in the residual fraction of the sludge, making it hard to extract. This work suggests that the biodegradable chelant GLDA, as potential substitute of the conventionally used EDTA, offers special insights in the effective removal of heavy metals from industrial sludge.

Acknowledgements

This work was supported by Innovation Scientists and Technicians Troop Construction Projects of Henan Province, Plan for Scientific Innovation Talent of Henan Province (Grant No. 134200510014), Key Scientific and Technological Project of Henan Province (Grant No. 142102310275), and Graduate Student Scientific Research Innovation Project of Henan Normal University (Grant No. YL201426).

References

- [1] C. Naoum, D. Fatta, K.J. Haralambous, M. Loidou, Removal of heavy metals from sewage sludge by acid treatment, *J. Environ. Sci. Health, A* 36 (2001) 873–881.
- [2] Z. L. Zhu, L. H. Zhang, H. Zhang, Y. L. Qiu, R. H. Zhang, J. F. Zhao, Extraction of cadmium from sewage sludge using polyepoxysuccinic acid, *Pedosphere* 19 (2009) 137–142.
- [3] Y. Bulut, Z. Te, Removal of heavy metals from aqueous solution by sawdust adsorption, *J. Environ. Sci.* 19 (2007) 160–166.
- [4] B. Yu, Y. Zhang, A. Shukla, S.S. Shukla, K.L. Dorris, The removal of heavy metal from aqueous solutions by sawdust adsorption removal of copper, *J. Hazard. Mater.* 80 (2000) 33–42.
- [5] S.E. Bailey, T.J. Olin, R.M. Bricka, D.D. Adrian, A review of potentially low cost sorbents for heavy metals, *Water Res.* 33 (1999) 2469–2479.
- [6] R. Wuana, F. Okieimen, J. Imborvungu, Removal of heavy metals from a contaminated soil using organic chelating acids, *Int. J. Environ. Sci. Technol.* 7 (2010) 485–496.
- [7] A.M. Chaudri, C.M. Allain, V.L. Barbosa Jefferson, F.A. Nicholson, B.J. Chambers, S.P. McGrath, A study of the impacts of Zn and Cu on two rhizobial species in soils of a long term field experiment, *Plant Soil* 221 (2000) 167–179.
- [8] M. Pueyo, G. Rauret, D. Lick, M. Yli-Halla, H. Muntau, P. Quevauviller, J. Lopez-Sanchez, Certification of the extractable contents of Cd, Cr, Cu, Ni, Pb and Zn in a freshwater sediment following a collaboratively tested and optimised three step sequential extraction procedure, *J. Environ. Monit.* 3 (2001) 243–250.
- [9] M.R. Dudinska, D.A. Clifford, Anion exchange studies of lead EDTA complexes, *React. Polym.* 16 (1991) 71–80.
- [10] R. S. Juang, L. D. Shiau, Ion exchange equilibria of metal chelates of ethylene diaminetetraacetic acid (EDTA) with Amberlite IRA 68, *Ind. Eng. Chem. Res.* 37 (1998) 555–560.
- [11] B. Sun, F. Zhao, E. Lombi, S. McGrath, Leaching of heavy metals from contaminated soils using EDTA, *Environ. Pollut.* 113 (2001) 111–120.
- [12] P. Vandevivere, F. Hammes, W. Verstraete, T. Feijtel, D. Schowanek, Metal

- [20] K. Y. Lee, K. W. Kim, Heavy metal removal from shooting range soil by hybrid electrokinetics with bacteria and enhancing agents, *Environ. Sci. Technol.* 44 (2010) 9482–9487.
- [21] M. Pueyo, J. Lopez Sanche, G. Rauret, Assessment of CaCl_2 , NaNO_3 and NH_4NO_3 extraction procedures for the study of Cd, Cu, Pb and Zn extractability in contaminated soils, *Anal. Chim. Acta* 504 (2004) 217–226.
- [22] E.A. Alvarez, M.C. Mochón, J. Sanche, M.T. Rodriguez, Heavy metal extractable forms in sludge from wastewater treatment plants, *Chemosphere* 47 (2002) 765–775.
- [23] A. Tessier, P.G. Campbell, M. Bisson, Sequential extraction procedure for the speciation of particulate trace metals, *Anal. Chem.* 51 (1979) 844–851.
- [24] P. Quevauviller, G. Rauret, J. Lopez Sanche, R. Rubio, A. Ure, H. Muntau, Certification of trace metal extractable contents in a sediment reference material (CRM 601) following a three step sequential extraction procedure, *Sci. Total Environ.* 205 (1997) 223–234.
- [25] C.M. Davidson, A.L. Duncan, D. Littlejohn, A.M. Ure, L.M. Garden, A critical evaluation of the three stage BCR sequential extraction procedure to assess the potential mobility and toxicity of heavy metals in industrially contaminated land, *Anal. Chim. Acta* 363 (1998) 45–55.
- [26] M.B. Arain, T.G. Kaik, M.K. Jamali, N. Jalbani, H.I. Afridi, J.A. Baig, Speciation of heavy metals in sediment by conventional, ultrasound and microwave assisted single extraction methods: a comparison with modified sequential extraction procedure, *J. Hazard. Mater.* 154 (2008) 998–1006.
- [27] D. Kodynska, Application of a new generation of complexing agents in removal of heavy metal ions from different wastes, *Environ. Sci. Pollut. Res.* 20 (2013) 5939–5949.
- [28] D. Kodynska, The effect of the novel complexing agent in removal of heavy metal ions from waters and waste waters, *Chem. Eng. J.* 165 (2010) 835–845.
- [29] B. Nowack, R. Schulz, B.H. Robinson, Critical assessment of chelant enhanced metal phytoextraction, *Environ. Sci. Technol.* 40 (2006) 5225–5232.
- [30] D.E. Guven, G. Akinci, Heavy metals partitioning in the sediments of Imir Inner Bay, *J. Environ. Sci.* 20 (2008) 413–418.